



Page 1 to 15

**POWER WIRES FOR CRIMPING,
LOW FREQUENCY, 600V, -200 TO +200 °C,
BASED ON TYPE SPP
ESCC Detail Specification No. 3901/017**

**ISSUE 2
August 2011**



Document Custodian: European Space Agency - see <https://escies.org>

	ESCC Detail Specification No. 3901/017		PAGE ii ISSUE 2
--	---	--	--------------------

LEGAL DISCLAIMER AND COPYRIGHT

European Space Agency, Copyright © 2011. All rights reserved.

The European Space Agency disclaims any liability or responsibility, to any person or entity, with respect to any loss or damage caused, or alleged to be caused, directly or indirectly by the use and application of this ESCC publication.

This publication, without the prior permission of the European Space Agency and provided that it is not used for a commercial purpose, may be:

- copied in whole, in any medium, without alteration or modification.
- copied in part, in any medium, provided that the ESCC document identification, comprising the ESCC symbol, document number and document issue, is removed.

DOCUMENTATION CHANGE NOTICE

DCR No.	CHANGE DESCRIPTION
630	Specification upissued to incorporate editorial and technical changes per DCR.

TABLE OF CONTENTS

		<u>Page</u>
1.	<u>GENERAL</u>	<u>5</u>
1.1	Scope	5
1.2	Type Variants	5
1.3	Maximum Ratings	5
1.4	Parameter Derating Information	5
1.5	Physical Characteristics	5
1.6	Functional Diagram	5
2.	<u>APPLICABLE DOCUMENTS</u>	<u>9</u>
3.	<u>TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS</u>	<u>9</u>
4.	<u>REQUIREMENTS</u>	<u>9</u>
4.1	General	9
4.2	Deviations from Generic Specification	9
4.2.1	Deviations from Special In-process Controls	9
4.2.2	Deviations from Final Production Tests	9
4.2.3	Deviations from Burn-in Tests	9
4.2.4	Deviations from Qualification Tests	9
4.2.5	Deviations from Lot Acceptance Tests	10
4.3	Mechanical Requirements	10
4.3.1	Dimension Check	10
4.3.2	Weight	10
4.4	Materials and Finishes	11
4.4.1	Conductor	11
4.4.2	Insulation	11
4.4.3	Colour-coding	12
4.5	Marking	12
4.5.1	General	12
4.5.2	The ESCC Component Number	12
4.5.3	Characteristics	12
4.5.4	Traceability Information	12
4.5.5	Additional Marking	12
4.6	Electrical Measurements	13
4.6.1	Electrical Measurements at Room Temperature	13
4.6.2	Electrical Measurements at High and Low Temperatures	13
4.6.3	Circuits for Electrical Measurements	13
4.7	Burn-in Tests	13
4.8	Environmental and Endurance Tests	13
4.8.1	Mechanical Properties of Conductor and Drain Wire	13
4.8.2	Accelerated Ageing	13
4.8.3	Wrap Test at Ambient Temperature	13
4.8.4	Voltage Test	13
4.8.5	Shrinkage	13
4.8.6	Blocking	13
4.8.7	Cold Bend Test	14
4.8.8	Cut-through Resistance	14
4.8.9	Notch Resistance	14
4.8.10	Flammability Resistance	14

	<u>Page</u>
4.8.11 Resistance to Fluids	14
4.8.12 Surface Resistance	14
4.8.13 Abrasion Resistance	14
4.8.14 Soldering	14
4.8.15 Solderability	14
4.8.16 Radiation Resistance	15
4.8.17 Overload Resistance	15
4.8.18 Outgassing in Vacuum	15
4.8.19 Long-term Ageing Test	15
4.8.20 Atomic Oxygen Resistance	15

TABLES

1(a) Type Variants	6
1(b) Maximum Ratings	7
A Mandrel Diameters and Loads for Finished Wires	13
B Mandrel Diameters and Loads for Shielded and Jacketed Cables	N/A
C Mandrel Diameters and Loads for Finished Wires or Cores	14
2 Electrical Measurements at Room Temperature	15

FIGURES

1 Parameter Derating Information	7
2 Physical Characteristics	8

APPENDICES (Applicable to specific Manufacturers only)

None



1. **GENERAL**

1.1 **SCOPE**

This specification details the ratings, physical and electrical characteristics, test and inspection data for Power Wires for Crimping, Low Frequency, 600V, -200 to +200 °C, based on Type SPP.

It shall be read in conjunction with ESCC Generic Specification No. 3901, the requirements of which are supplemented herein.

1.2 **TYPE VARIANTS**

Variants of the basic types of wires specified herein, which are also covered by this specification, are listed in Table 1(a).

1.3 **MAXIMUM RATINGS**

The maximum ratings, applicable to the finished wires specified herein, which shall not be exceeded at any time during use or storage in controlled space environment, are scheduled in Table 1(b).

1.4 **PARAMETER DERATING INFORMATION**

The derating information applicable to the finished wires and cables specified herein is as follows:

- The maximum current for each wire used in a bundle shall be:-

$$I_{Bmax} = I_{max} \frac{29 - n}{28} \quad (\text{for } 1 \leq n \leq 15)$$

$$I_{Bmax} = \frac{I_{max}}{2} \quad (\text{for } n > 15)$$

where n = number of wires in the bundle;

- The temperature derating information is shown in Figure 1 with maximum current I_{max} for a single wire.
- The derating factors contained herein indicate maximum stress values and do not preclude further derating.

1.5 **PHYSICAL CHARACTERISTICS**

The physical characteristics of the cables specified herein are shown in Figure 2 and Table 1(a).

1.6 **FUNCTIONAL DIAGRAM**

Not applicable.

TABLE 1(a) - TYPE VARIANTS

VARIANT No.	WIRE SIZE AWG	STRANDING No. OF STRANDS x DIAMETER (mm)	CONDUCTOR CHARACTERISTICS			FINISHED CABLE CHARACTERISTICS	
			MAX Ø (mm)	NOM SECT. (mm ²)	MAX OHMIC RESISTANCE (Ω/km)	MAX Ø (mm)	MAX WEIGHT (kg/km)
01	0	19x55x0.254RC	10.5	53	0.38	11.8	542
02	4	19x7x0.454RU	6.5	22	0.91	7.7	232
03	8	19x7x0.287RC	4.2	8.6	2.38	5.3	98

NOTES 1. RC = rope lay; RU = rope unilay.



TABLE 1(b) - MAXIMUM RATINGS

NO	CHARACTERISTICS	SYMBOL	MAXIMUM RATING	UNIT	REMARKS
1	Voltage	V_P	600	Vrms	
2	Maximum Current (Note 1)	I_{max}	45 81 133	A	For AWG 8 4 0
3	Operating Temperature Range	T_{amb}	-200 to +200	°C	
4	Storage Temperature Range	T_{stg}	-200 to +200	°C	

NOTES

- The above specified current will generate a temperature rise of approximately 50°C above ambient temperature in a vacuum environment. Precautions shall be taken to prevent the total temperature of the wire (ambient plus rise) exceeding the continuous operating temperature of the wire.

FIGURE 1 - PARAMETER DERATING INFORMATION


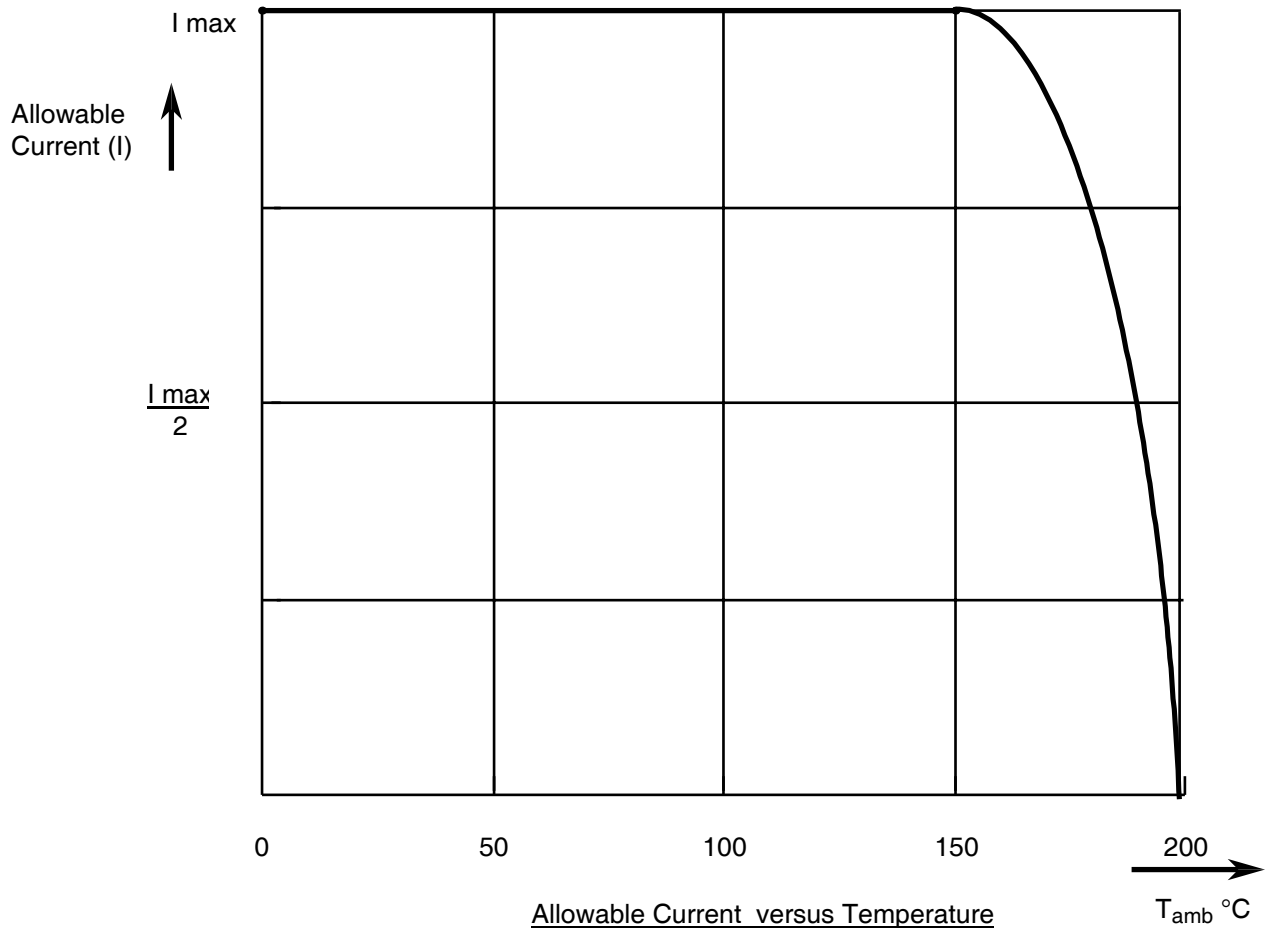


FIGURE 2 - PHYSICAL CHARACTERISTICS

Dimensions are given in Table 1(a)

FINISHED WIRES

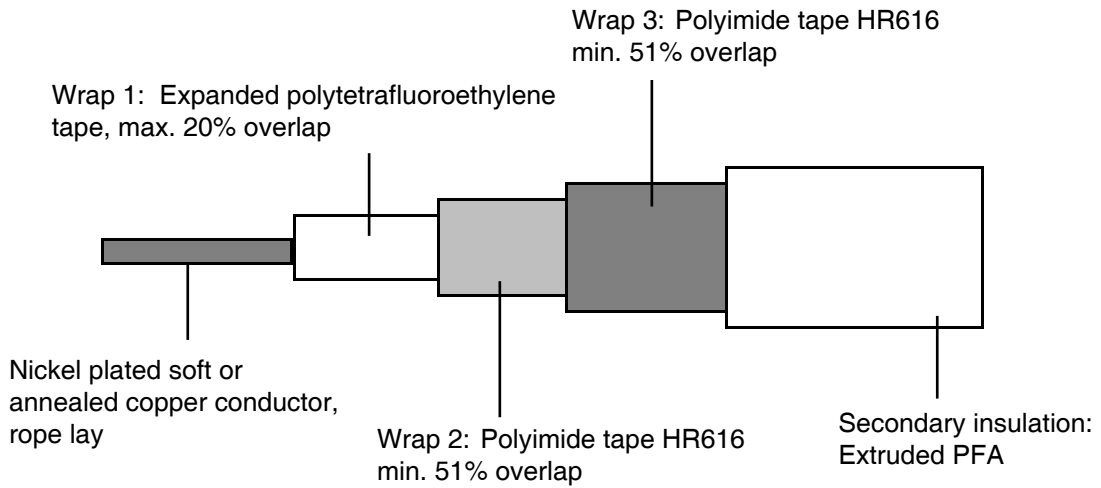

	<p style="text-align: center;">ESCC Detail Specification No. 3901/017</p>	<p>PAGE 9 ISSUE 2</p>
---	---	---------------------------

2. **APPLICABLE DOCUMENTS**

The following documents form part of this specification and shall be read in conjunction with it:

- ESCC Generic Specification No. 3901, Wires and Cables, Electrical, 600V, Low Frequency.
- ASTM B355, Standard Specification for Nickel Coated Soft or Annealed Copper Wire.

3. **TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS**

For the purpose of this specification, the terms, definitions, abbreviations, symbols and units specified in ESCC Basic Specification No. 21300 and ESCC Generic Specification No. 3901 shall apply.

4. **REQUIREMENTS**

4.1 **GENERAL**

The complete requirements for procurement of the finished wires specified herein are stated in this specification and ESCC Generic Specification No. 3901. Deviations from the Generic Specification, applicable to this specification only, are listed in Para 4.2.

Deviations from the applicable Generic Specification and this Detail Specification, formally agreed with specific Manufacturers on the basis that the alternative requirements are equivalent to the ESCC requirements and do not affect the components reliability, are listed in the Appendices attached to this specification.

4.2 **DEVIATIONS FROM GENERIC SPECIFICATION**

4.2.1 **Deviations from Special In-process Controls**

None.

4.2.2 **Deviations from Final Production Tests (Chart II)**

(a) Para. 9.25, Solderability: Not applicable.

4.2.3 **Deviations from Burn-in Tests (Chart III)**

Not applicable.

4.2.4 **Deviations from Qualification Tests (Chart IV)**

(a) Para. 9.15, Shrinkage shall be less than 5mm.

(b) Para. 9.24, Soldering: Not applicable.

(c) Para. 9.25, Solderability: Not applicable.

(d) Para.9.10, Anthony & Brown test: Not applicable

(e) Para. 9.12, Accelerated Ageing: Para. 9.12.2 is applicable.

(f) Para. 9.29, Long-term Ageing: test samples shall be aged as free coils (as per Para. 9.12.2).

4.2.5 Deviations from Lot Acceptance Tests (Chart V)

- (a) Para. 9.24, Soldering: Not applicable.
- (b) Para.9.10, Anthony & Brown test: Not applicable.
- (c) Para. 9.15, Shrinkage shall be less than 5mm.
- (d) Para. 9.25, Solderability: Not applicable.
- (e) Para. 9.12, Accelerated Ageing: Para. 9.12.2 is applicable.

4.3 MECHANICAL REQUIREMENTS

4.3.1 Dimension Check

The dimensions of the finished wires specified herein shall be checked; they shall conform to those shown in Table 1(a), Figure 2 and Para 4.4 of this specification (see below for the list of parameters to be checked).

LIST OF PARAMETERS TO BE CHECKED

PARAMETER	TABLE 1(a)	FIGURE 2	PARA 4.4
<u>COMPOSITION</u>			
Gauge	X		
Insulation		X	
Jacket		X	
<u>CONDUCTOR</u>			
Nature			X
Outer diameter	X		
Number of strands	X		
Strand diameter	X		
Length of lay			X
Nickel thickness			X
<u>INSULATION</u>			
Composition		X	X
Thickness			X
Concentricity			X
Outer diameter	X		
Core identification			X

4.3.2 Weight

The maximum weight of the finished wires specified herein shall be as specified in Table 1(a).

	<p style="text-align: center;">ESCC Detail Specification No. 3901/017</p>	<p style="text-align: right;">PAGE 11 ISSUE 2</p>
---	---	---

4.4 MATERIALS AND FINISHES

The materials and finishes shall be as specified herein. Where a definite material is not specified, a material which will enable the wires specified herein to meet the performance requirements of this specification shall be used. Acceptance or approval of any constituent material does not guarantee acceptance of the finished product.

4.4.1 Conductor

4.4.1.1 Material Characteristics

All strands used in the manufacture of the conductors shall be nickel plated, oxygen free copper from AWG 0 to 8. On the nickel plated strands the thickness of the nickel shall be 1.2µm minimum.

On all nickel plated copper conductors, any strand shall show a 10% minimum elongation.

4.4.1.2 Stranding

The conductors shall be rope lay as specified in Table 1(a). Strand and rope members shall be concentrically stranded using unilay concentric (commonly known as "unilay") or counter directional concentric (commonly known as "concentric") constructions.

Concentric stranding shall be defined as a central core surrounded by one or more layers of helically wound strands in a fixed round geometric arrangement.

In "unilay" constructions the successive layers have the same lay direction and lay length.

In "concentric" constructions the lay direction of successive layers are alternately reversed with increasing lay lengths.

The length of lay of the outer layer of stranded members forming the conductor shall be maximum:

- 127mm for AWG 0.
- 77mm for AWG 4.
- 51mm for AWG 8.

In all cases the standard direction of lay of the outer layer is left hand.

4.4.2 Insulation

4.4.2.1 Material

The primary insulating material shall be polyimide over expanded polytetrafluoroethylene, both with only those additives that are necessary for processing.

The secondary insulation material shall be virgin perfluoralcoxycopolymer with only those additives that are necessary for processing and pigmentation.

4.4.2.2 Construction

The insulation shall have a uniform cross-section throughout the length of the cable and the conductor shall be evenly centred in the insulation.

The insulation shall consist of 1 wrapped layer of expanded polytetrafluoroethylene tape and 2 wrapped layers of polyimide tapes as specified in Figure 2.



4.4.3 Colour Coding

The colour of the finished wires shall be the following colours of the secondary insulation.

Colours:

- AWG 8: Red.
- AWG 4: Yellow.
- AWG 0: Blue

4.5 MARKING


4.5.1 General

The marking of all spools of finished wires delivered to this specification shall be in accordance with the requirements of ESCC Basic Specification No. 21700. Each spool shall be marked in respect of:-

- (a) The ESCC Component Number.
- (b) Characteristics.
- (c) Traceability Information.
- (d) Additional Marking.


4.5.2 The ESCC Component Number

Each spool shall bear the ESCC Component Number which shall be constituted and marked as follows:-

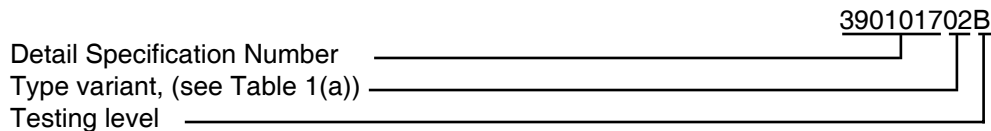

4.5.3 Characteristics

The characteristics shall show the length(s) of the finished wire wound on each spool and shall be



NOTES

1. Whenever the length is less than 100 metres, insert a zero in the first block (example: 075 m). If more than one length of finished wire or cable is wound on a spool, the characteristics of each length shall be marked as above.

4.5.4 Traceability Information

Each spool shall be marked in respect of traceability information in accordance with the requirements of ESCC Basic Specification No. 21700.

4.5.5 Additional Marking

Each spool shall bear the Manufacturers Quality Control Inspectors stamp.



4.6 ELECTRICAL MEASUREMENTS

4.6.1 Electrical Measurements at Room Temperature

The parameters to be measured at room temperature are scheduled in Table 2. The measurements shall be performed at $T_{amb} = +22 \pm 3$ °C.

4.6.2 Electrical Measurements at High and Low Temperatures

Not applicable.

4.6.3 Circuits for Electrical Measurements

Not applicable.

4.7 BURN-IN TESTS

Not applicable.

4.8 ENVIRONMENTAL AND ENDURANCE TESTS

4.8.1 Mechanical Properties of Conductor

As detailed in Para. 4.4.1.1 of this specification.

4.8.2 Accelerated Ageing

Ageing Temperature $+230 \pm 5$ °C.

4.8.3 Wrap Test at Ambient Temperature

The mandrel diameters and applied loads for wrap testing of finished wires are given in Table A.

TABLE A - MANDREL DIAMETERS AND LOADS FOR FINISHED WIRES

Wire Size AWG	Mandrel Diameter (mm)	Applied Weight (kg)
0	100	3.5
4	75	1.8
8	50	1.3

TABLE B - MANDREL DIAMETERS AND LOADS FOR SHIELDED AND JACKETED CABLES

Not applicable.

4.8.4 Voltage Test

No particular conditions are applicable.

4.8.5 Shrinkage

The shrinkage temperature shall be $+200 \pm 5$ °C. The shrinkage shall be according to Para. 4.2.4. of this specification

4.8.6 Blocking

The blocking temperature shall be $+230 \pm 5$ °C. Cooling down to room temperature: 16 hours for AWG 0 and 4.

4.8.7 Cold Bend Test

The mandrel diameters and loads shall be as specified in Table C.

TABLE C - MANDREL DIAMETERS AND LOADS FOR FINISHED WIRES

Wire Size AWG	Mandrel Diameter (mm)	Applied Weight (kg)
0	80	3.5
4	60	1.8
8	30	1.3

4.8.8 Cut-through Resistance

The mean load measured during 9 tests shall not be less than the relevant value specified below:-

Wire Size AWG Requirements	0	4	8
Cut-through Load (N)	1200	680	800

4.8.9 Notch Resistance

The depth of notch shall be 0.1mm.

4.8.10 Flammability Resistance

No particular conditions are applicable.

4.8.11 Resistance to Fluids

No particular conditions are applicable.

4.8.12 Surface Resistance

No particular conditions are applicable.

4.8.13 Abrasion Resistance

The weight to be applied to the needle is specified below:-

Wire Size AWG Requirements	0	4	8
Scrape Abrasion (Load in N)	35	17	12

4.8.14 Soldering

Not applicable.

4.8.15 Solderability

Not applicable.

4.8.16 Radiation Resistance

No particular conditions are applicable.

4.8.17 Overload Resistance

No particular conditions are applicable.

4.8.18 Outgassing in Vacuum

No particular conditions are applicable.

4.8.19 Long-term Ageing Test

The long-term ageing temperature shall be $+200 \pm 5^{\circ}\text{C}$.

4.8.20 Atomic Oxygen Resistance

The outer surface of the single insulated wires and the jackets of the cables are resistant against atomic oxygen and shall be verified according to the requirements of the ESCC Executive.

TABLE 2 - ELECTRICAL MEASUREMENTS AT ROOM TEMPERATURE

NO	CHARACTERISTICS	SPECIFICATION AND TEST METHOD	TEST CONDITION	LIMITS	UNIT
1	Conductor Resistance	ESCC No. 3901, Section 9	Para 9.5	Table 1(a)	Ω/km
2	Spark Test	ESCC No. 3901, Section 9	Para 9.6	Insulation: 3	kV
3	Voltage Test	ESCC No. 3901, Section 9	Para 9.7	Para 9.7	kV
4	Insulation Resistance	ESCC No. 3901, Section 9	Para 9.8	Insulation: 750	$\text{M}\Omega.\text{km}$
5	Surface Resistance	ESCC No. 3901, Section 9	Para 9.22	125	$\text{M}\Omega.\text{mm}$