



Page 1 to 20

POLYIMIDE INSULATED WIRES AND CABLES,

LOW FREQUENCY, 600V, -200 TO +200 °C,

BASED ON TYPE SPL

ESCC Detail Specification No. 3901/019

ISSUE 2

August 2011



Document Custodian: European Space Agency - see <https://escies.org>

| | | | |
|--|---|--|--------------------|
|  | ESCC Detail Specification No. 3901/019 | | PAGE ii ISSUE 2 |
|--|---|--|--------------------|

LEGAL DISCLAIMER AND COPYRIGHT

European Space Agency, Copyright © 2011. All rights reserved.

The European Space Agency disclaims any liability or responsibility, to any person or entity, with respect to any loss or damage caused, or alleged to be caused, directly or indirectly by the use and application of this ESCC publication.

This publication, without the prior permission of the European Space Agency and provided that it is not used for a commercial purpose, may be:

- copied in whole, in any medium, without alteration or modification.
- copied in part, in any medium, provided that the ESCC document identification, comprising the ESCC symbol, document number and document issue, is removed.



DOCUMENTATION CHANGE NOTICE

| DCR No. | CHANGE DESCRIPTION |
|---------|--|
| 630 | Specification upissued to incorporate editorial and technical changes per DCR. |


| | | | |
|---|---|--|---------------------------|
|  | <p style="text-align: center;">ESCC Detail Specification No. 3901/019</p> | | <p>PAGE 3 ISSUE 2</p> |
|---|---|--|---------------------------|

TABLE OF CONTENTS

| | | <u>Page</u> |
|-----------|--|-------------|
| 1. | <u>GENERAL</u> | 5 |
| 1.1 | Scope | 5 |
| 1.2 | Type Variants | 5 |
| 1.3 | Maximum Ratings | 5 |
| 1.4 | Parameter Derating Information | 5 |
| 1.5 | Physical Characteristics | 5 |
| 1.6 | Functional Diagram | 5 |
| 2. | <u>APPLICABLE DOCUMENTS</u> | 12 |
| 3. | <u>TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS</u> | 12 |
| 4. | <u>REQUIREMENTS</u> | 12 |
| 4.1 | General | 12 |
| 4.2 | Deviations from Generic Specification | 12 |
| 4.2.1 | Deviations from Special In-process Controls | 12 |
| 4.2.2 | Deviations from Final Production Tests | 12 |
| 4.2.3 | Deviations from Burn-in Tests | 12 |
| 4.2.4 | Deviations from Qualification Tests | 12 |
| 4.2.5 | Deviations from Lot Acceptance Tests | 12 |
| 4.3 | Mechanical Requirements | 13 |
| 4.3.1 | Dimension Check | 13 |
| 4.3.2 | Weight | 13 |
| 4.4 | Materials and Finishes | 14 |
| 4.4.1 | Conductor | 14 |
| 4.4.2 | Insulation | 14 |
| 4.4.3 | Shield | 14 |
| 4.4.4 | Jacket | 15 |
| 4.4.5 | Construction of Multicore Cables | 15 |
| 4.4.6 | Colour-coding | 15 |
| 4.5 | Marking | 16 |
| 4.5.1 | General | 16 |
| 4.5.2 | The ESCC Component Number | 16 |
| 4.5.3 | Characteristics | 16 |
| 4.5.4 | Traceability Information | 17 |
| 4.5.5 | Additional Marking | 17 |
| 4.6 | Electrical Measurements | 17 |
| 4.6.1 | Electrical Measurements at Room Temperature | 17 |
| 4.6.2 | Electrical Measurements at High and Low Temperatures | 17 |
| 4.6.3 | Circuits for Electrical Measurements | 17 |
| 4.7 | Burn-in Tests | 17 |
| 4.8 | Environmental and Endurance Tests | 17 |
| 4.8.1 | Mechanical Properties of Conductor and Drain Wire | 17 |
| 4.8.2 | Accelerated Ageing | 17 |
| 4.8.3 | Wrap Test at Ambient Temperature | 17 |
| 4.8.4 | Voltage Test | 19 |
| 4.8.5 | Shrinkage | 19 |
| 4.8.6 | Blocking | 19 |
| 4.8.7 | Cold Bend Test | 19 |
| 4.8.8 | Cut-through Resistance | 19 |
| 4.8.9 | Notch Resistance | 19 |
| 4.8.10 | Flammability Resistance | 19 |



| | <u>Page</u> |
|------------------------------|-------------|
| 4.8.11 Resistance to Fluids | 19 |
| 4.8.12 Surface Resistance | 19 |
| 4.8.13 Abrasion Resistance | 20 |
| 4.8.14 Soldering | 20 |
| 4.8.15 Solderability | 20 |
| 4.8.16 Radiation Resistance | 20 |
| 4.8.17 Overload Resistance | 20 |
| 4.8.18 Outgassing in Vacuum | 20 |
| 4.8.20 Long-term Ageing Test | 20 |

TABLES

| | |
|--|----|
| 1(a) Type Variants | 6 |
| 1(b) Maximum Ratings | 10 |
| A Mandrel Diameters and Loads for Finished Wires | 17 |
| B Mandrel Diameters and Loads for Shielded and Jacketed Cables | 18 |
| C Mandrel Diameters and Loads for Finished Wires or Cores | 19 |
| 2 Electrical Measurements at Room Temperature | 20 |

FIGURES

| | |
|----------------------------------|----|
| 1 Parameter Derating Information | 10 |
| 2 Physical Characteristics | 11 |

APPENDICES (Applicable to specific Manufacturers only)

None



1. **GENERAL**

1.1 **SCOPE**

This specification details the ratings, physical and electrical characteristics, test and inspection data for Polyimide Insulated Wires and Cables, Low Frequency, 600V, -200 to +200 °C, based on Type SPL.

It shall be read in conjunction with ESCC Generic Specification No. 3901, the requirements of which are supplemented herein.

NOTES

1. These wires and cables shall not be used in the presence or vicinity of hydrazine or nitrogen tetroxide.
2. These wires and cables are light versions of SPC types according to ESCC Detail Specification No. 3901/009; they are identical in production and test with the following exceptions:

- Conductor according to ISO 2635 (except AWG 28)
- Shield size # 40
- Shield type served wire shield (SWS)

This leads to savings in diameter and weight according to Table 1(a).

1.2 **TYPE VARIANTS**

Variants of the basic types of wires and cables specified herein, which are also covered by this specification, are listed in Table 1(a).

1.3 **MAXIMUM RATINGS**

The maximum ratings, applicable to the finished wires and cables specified herein, which shall not be exceeded at any time during use or storage in controlled space environment, are scheduled in Table 1(b).

1.4 **PARAMETER DERATING INFORMATION**

The derating information applicable to the finished wires and cables specified herein is as follows:

- The maximum current for each wire used in a bundle shall be:-

$$I_{Bmax} = I_{max} \times \frac{29 - n}{28} \quad (\text{for } 1 \leq n \leq 15)$$

$$I_{Bmax} = \frac{I_{max}}{2} \quad (\text{for } n > 15)$$

- The temperature derating information is shown in Figure 1 with maximum current I_{max} for a single wire.
- The derating factors contained herein indicate maximum stress values and do not preclude further derating.

1.5 **PHYSICAL CHARACTERISTICS**

The physical characteristics of the wires and cables specified herein are shown in Figure 2 and Table 1(a).

1.6 **FUNCTIONAL DIAGRAM**

Not applicable.

TABLE 1(a) - TYPE VARIANTS

| VARIANT No. | SHIELDED | | No. OF CORES | WIRE SIZE ISO/ (AWG) | STRANDING No. OF STRANDS x DIAMETER (mm) | CONDUCTOR CHARACTERISTICS | | | SHIELD STRAND DIA (mm) | CORE MAX DIA (mm) | FINISHED WIRE OR CABLE CHARACTERISTICS | |
|-------------|----------|----|--------------|----------------------|--|---------------------------|------------------------------|-----------------------------|------------------------|-------------------|--|--------------------|
| | YES | NO | | | | MAX DIA (mm) | NOM SECT. (mm ²) | MAX OHMIC RESISTANCE (Ω/km) | | | MAX DIA (mm) | MAX WEIGHT (kg/km) |
| 01 | | X | 1 | -/(30) | 7x0.102 | 0.32 | 0.057 | 375 | | | 0.78 | 0.98 |
| 02 | | X | 1 | -/(28) | 7x0.127 | 0.47 | 0.09 | 253 | | | 0.87 | 1.4 |
| 03 | | X | 1 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 157 | | | 0.96 | 1.9 |
| 04 | | X | 1 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 111 | | | 1.13 | 2.6 |
| 05 | | X | 1 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 58 | | | 1.25 | 3.9 |
| 06 | | X | 1 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 32 | | | 1.48 | 6.4 |
| 07 | | X | 1 | 012/(16) | 19x0.30 (1) | 1.49 | 1.20 | 14 | | | 1.98 | 13 |
| 08 | | X | 1 | 030/(12) | 37x0.32 (1) | 2.18 | 3.00 | 7.0 | | | 2.73 | 27 |
| 09 | | X | 2 | -/(30) | 7x0.102 | 0.32 | 0.057 | 383 | | 0.78 | 1.5 | 2.1 |
| 10 | | X | 2 | -/(28) | 7x0.127 | 0.47 | 0.09 | 258 | | 0.87 | 1.7 | 2.8 |
| 11 | | X | 2 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 170 | | 0.96 | 1.9 | 3.8 |
| 12 | | X | 2 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 120 | | 1.13 | 2.3 | 5.2 |
| 13 | | X | 2 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 63 | | 1.25 | 2.5 | 8.2 |
| 14 | | X | 2 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 35 | | 1.48 | 3.0 | 13.5 |
| 15 | | X | 2 | 012/(16) | 19x0.30 (1) | 1.49 | 1.20 | 15 | | 1.98 | 4.0 | 27.0 |
| 16 | | X | 2 | 030/(12) | 37x0.32 (1) | 2.18 | 3.00 | 7.5 | | 2.73 | 5.5 | 55.0 |
| 17 | | X | 3 | -/(30) | 7x0.102 | 0.32 | 0.057 | 384 | | 0.78 | 1.7 | 3.3 |
| 18 | | X | 3 | -/(28) | 7x0.127 | 0.47 | 0.09 | 259 | | 0.87 | 1.9 | 4.5 |
| 19 | | X | 3 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 171 | | 0.96 | 2.1 | 6.2 |
| 20 | | X | 3 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 121 | | 1.13 | 2.5 | 8.3 |
| 21 | | X | 3 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 64 | | 1.25 | 2.7 | 12.7 |
| 22 | | X | 3 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 37 | | 1.48 | 3.2 | 20.6 |
| 23 | | X | 3 | 012/(16) | 19x0.30 (1) | 1.49 | 1.20 | 15 | | 1.98 | 4.3 | 43.0 |
| 24 | | X | 3 | 030/(12) | 37x0.32 (1) | 2.18 | 3.00 | 7.5 | | 2.73 | 5.9 | 88.0 |

NOTES: See Page 9.

TABLE 1(a) - TYPE VARIANTS

| VARIANT No. | SHIELDED | | No. OF CORES | WIRE SIZE ISO/ (AWG) | STRANDING No. OF STRANDS x DIAMETER (mm) | CONDUCTOR CHARACTERISTICS | | | SHIELD STRAND DIA (mm) | CORE MAX DIA (mm) | FINISHED WIRE OR CABLE CHARACTERISTICS | |
|-------------|----------|----|--------------|----------------------|--|---------------------------|------------------------------|-----------------------------|------------------------|-------------------|--|--------------------|
| | YES | NO | | | | MAX DIA (mm) | NOM SECT. (mm ²) | MAX OHMIC RESISTANCE (Ω/km) | | | MAX DIA (mm) | MAX WEIGHT (kg/km) |
| 25 | | X | 4 | -(30) | 7x0.102 | 0.32 | 0.057 | 385 | | 0.78 | 1.9 | 4.4 |
| 26 | | X | 4 | -(28) | 7x0.127 | 0.47 | 0.09 | 260 | | 0.87 | 2.1 | 6.0 |
| 27 | | X | 4 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 171 | | 0.96 | 2.3 | 8.2 |
| 28 | | X | 4 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 122 | | 1.13 | 2.7 | 11.0 |
| 29 | | X | 4 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 64 | | 1.25 | 3.0 | 16.9 |
| 30 | | X | 4 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 37 | | 1.48 | 3.6 | 27.3 |
| 31 | | X | 4 | 012/(16) | 19x0.30 (1) | 1.49 | 1.20 | 16 | | 1.98 | 4.8 | 57.0 |
| 32 | | X | 4 | 030/(12) | 37x0.32 (1) | 2.18 | 3.00 | 7.9 | | 2.73 | 6.5 | 118 |
| 33 | | X | 5 | -(28) | 7x0.127 | 0.47 | 0.09 | 260 | | 0.87 | 2.4 | 7.8 |
| 34 | | X | 5 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 172 | | 0.96 | 2.6 | 10.7 |
| 35 | | X | 5 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 123 | | 1.13 | 3.1 | 14.3 |
| 36 | | X | 5 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 64 | | 1.25 | 3.4 | 21.8 |
| 37 | | X | 5 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 37 | | 1.48 | 4.0 | 35.0 |
| 38 | | X | 6 | -(28) | 7x0.127 | 0.47 | 0.09 | 261 | | 0.87 | 2.6 | 9.6 |
| 39 | | X | 6 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 172 | | 0.96 | 2.9 | 13.1 |
| 40 | | X | 6 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 124 | | 1.13 | 3.4 | 17.6 |
| 41 | | X | 6 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 65 | | 1.25 | 3.7 | 26.6 |
| 42 | | X | 6 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 38 | | 1.48 | 4.4 | 48.2 |
| 43 | | X | 7 | -(28) | 7x0.127 | 0.47 | 0.09 | 261 | | 0.87 | 2.6 | 10.5 |
| 44 | | X | 7 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 172 | | 0.96 | 2.9 | 14.4 |
| 45 | | X | 7 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 124 | | 1.13 | 3.4 | 19.3 |
| 46 | | X | 7 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 65 | | 1.25 | 3.7 | 29.6 |
| 47 | | X | 7 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 38 | | 1.48 | 4.4 | 47.8 |

NOTES: See Page 9.

TABLE 1(a) - TYPE VARIANTS

| VARIANT No. | SHIELDED | | No. OF CORES | WIRE SIZE ISO/ (AWG) | STRANDING No. OF STRANDS x DIAMETER (mm) | CONDUCTOR CHARACTERISTICS | | | SHIELD STRAND DIA (mm) | CORE MAX DIA (mm) | FINISHED WIRE OR CABLE CHARACTERISTICS | |
|-------------|----------|----|--------------|----------------------|--|---------------------------|------------------------------|-----------------------------|------------------------|-------------------|--|--------------------|
| | YES | NO | | | | MAX DIA (mm) | NOM SECT. (mm ²) | MAX OHMIC RESISTANCE (Ω/km) | | | MAX DIA (mm) | MAX WEIGHT (kg/km) |
| 48 | x | | 1 | -/(30) | 7x0.102 | 0.32 | 0.057 | 375 | 0.063 | 0.78 | 1.1 | 2.6 |
| 49 | x | | 1 | -/(28) | 7x0.127 | 0.47 | 0.09 | 253 | 0.079 | 0.87 | 1.2 | 3.3 |
| 50 | x | | 1 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 157 | 0.079 | 0.96 | 1.3 | 4.1 |
| 51 | x | | 1 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 111 | 0.079 | 1.13 | 1.5 | 4.8 |
| 52 | x | | 1 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 58 | 0.079 | 1.25 | 1.6 | 6.3 |
| 53 | x | | 1 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 32 | 0.079 | 1.48 | 1.9 | 9.1 |
| 54 | x | | 1 | 012/(16) | 19x0.30 (1) | 1.49 | 1.20 | 14 | 0.079 | 1.98 | 2.4 | 16.8 |
| 55 | x | | 1 | 030/(12) | 37x0.32 (1) | 2.18 | 3.00 | 7.0 | 0.079 | 2.73 | 3.1 | 31.7 |
| 56 | x | | 2 | -/(30) | 7x0.102 | 0.32 | 0.057 | 383 | 0.063 | 0.78 | 1.9 | 5.1 |
| 57 | x | | 2 | -/(28) | 7x0.127 | 0.47 | 0.09 | 258 | 0.079 | 0.87 | 2.1 | 6.1 |
| 58 | x | | 2 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 170 | 0.079 | 0.96 | 2.3 | 7.7 |
| 59 | x | | 2 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 120 | 0.079 | 1.13 | 2.7 | 9.5 |
| 60 | x | | 2 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 63 | 0.079 | 1.25 | 2.9 | 13.4 |
| 61 | x | | 2 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 35 | 0.079 | 1.48 | 3.3 | 19.6 |
| 62 | x | | 2 | 012/(16) | 19x0.30 (1) | 1.49 | 1.20 | 15 | 0.079 | 1.98 | 4.3 | 35.0 |
| 63 | x | | 2 | 030/(12) | 37x0.32 (1) | 2.18 | 3.00 | 7.5 | 0.079 | 2.73 | 5.8 | 67.0 |
| 64 | x | | 3 | -/(30) | 7x0.102 | 0.32 | 0.057 | 385 | 0.063 | 0.78 | 2.0 | 6.1 |
| 65 | x | | 3 | -/(28) | 7x0.127 | 0.47 | 0.09 | 259 | 0.079 | 0.87 | 2.3 | 8.3 |
| 66 | x | | 3 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 171 | 0.079 | 0.96 | 2.4 | 10.3 |
| 67 | x | | 3 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 121 | 0.079 | 1.13 | 2.8 | 13.2 |
| 68 | x | | 3 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 64 | 0.079 | 1.25 | 3.1 | 18.0 |
| 69 | x | | 3 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 37 | 0.079 | 1.48 | 3.6 | 26.8 |
| 70 | x | | 3 | 012/(16) | 19x0.30 (1) | 1.49 | 1.20 | 15 | 0.079 | 1.98 | 4.6 | 51.0 |
| 71 | x | | 3 | 030/(12) | 37x0.32 (1) | 2.18 | 3.00 | 7.5 | 0.079 | 2.73 | 6.2 | 99.0 |

TABLE 1(a) - TYPE VARIANTS

| VARIANT No. | SHIELDED | | No. OF CORES | WIRE SIZE ISO/ (AWG) | STRANDING No. OF STRANDS x DIAMETER (mm) | CONDUCTOR CHARACTERISTICS | | | SHIELD STRAND DIA (mm) | CORE MAX DIA (mm) | FINISHED WIRE OR CABLE CHARACTERISTICS | |
|-------------|----------|----|--------------|----------------------|--|---------------------------|------------------------------|-----------------------------|------------------------|-------------------|--|--------------------|
| | YES | NO | | | | MAX DIA (mm) | NOM SECT. (mm ²) | MAX OHMIC RESISTANCE (Ω/km) | | | MAX DIA (mm) | MAX WEIGHT (kg/km) |
| 72 | X | | 4 | -(/30) | 7x0.102 | 0.32 | 0.057 | 386 | 0.063 | 0.78 | 2.2 | 7.6 |
| 73 | X | | 4 | -(/28) | 7x0.127 | 0.47 | 0.09 | 260 | 0.079 | 0.87 | 2.5 | 10.4 |
| 74 | X | | 4 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 171 | 0.079 | 0.96 | 2.7 | 12.2 |
| 75 | X | | 4 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 122 | 0.079 | 1.13 | 3.1 | 16.4 |
| 76 | X | | 4 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 64 | 0.079 | 1.25 | 3.4 | 22.9 |
| 77 | X | | 4 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 37 | 0.079 | 1.48 | 3.9 | 34.4 |
| 78 | X | | 4 | 012/(16) | 19x0.30 (1) | 1.49 | 1.20 | 16 | 0.079 | 1.98 | 5.1 | 63.0 |
| 79 | X | | 4 | 030/(12) | 37x0.32 (1) | 2.18 | 3.00 | 7.9 | 0.079 | 2.73 | 6.9 | 124 |
| 80 | X | | 5 | -(/28) | 7x0.127 | 0.47 | 0.09 | 260 | 0.079 | 0.87 | 2.7 | 12.5 |
| 81 | X | | 5 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 172 | 0.079 | 0.96 | 2.9 | 15.8 |
| 82 | X | | 5 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 123 | 0.079 | 1.13 | 3.4 | 20.4 |
| 83 | X | | 5 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 64 | 0.079 | 1.25 | 3.7 | 28.4 |
| 84 | X | | 5 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 37 | 0.079 | 1.48 | 4.4 | 43.0 |
| 85 | X | | 6 | -(/28) | 7x0.127 | 0.47 | 0.09 | 261 | 0.079 | 0.87 | 3.0 | 14.8 |
| 86 | X | | 6 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 172 | 0.079 | 0.96 | 3.2 | 18.8 |
| 87 | X | | 6 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 124 | 0.079 | 1.13 | 3.8 | 24.3 |
| 88 | X | | 6 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 65 | 0.079 | 1.25 | 4.1 | 34.0 |
| 89 | X | | 6 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 38 | 0.079 | 1.48 | 4.8 | 58.2 |
| 90 | X | | 7 | -(/28) | 7x0.127 | 0.47 | 0.09 | 261 | 0.079 | 0.87 | 3.0 | 15.7 |
| 91 | X | | 7 | 001/(26) | 19x0.1 (1) | 0.57 | 0.15 | 172 | 0.079 | 0.96 | 3.2 | 20.1 |
| 92 | X | | 7 | 002/(24) | 19x0.12 (1) | 0.58 | 0.25 | 124 | 0.079 | 1.13 | 3.8 | 26.0 |
| 93 | X | | 7 | 004/(22) | 19x0.15 (1) | 0.76 | 0.40 | 65 | 0.079 | 1.25 | 4.1 | 37.0 |
| 94 | X | | 7 | 006/(20) | 19x0.20 (1) | 0.99 | 0.60 | 38 | 0.079 | 1.48 | 4.8 | 57.0 |

NOTES 1. According to ISO 2653 (AWG sizes given for information).




TABLE 1(b) - MAXIMUM RATINGS

| NO | CHARACTERISTICS | SYMBOL | MAXIMUM RATING | UNIT | REMARKS |
|----|-----------------------------|-----------|---|------|--|
| 1 | Voltage | V_P | 600 | Vrms | |
| 2 | Maximum Current (Note 1) | I_{max} | 1.5 2.5 3.5 5.0 7.5 13 23 | A | For AWG 28 26 24 22 20 16 12 |
| 3 | Operating Temperature Range | T_{amb} | -200 to +200 | °C | |
| 4 | Storage Temperature Range | T_{stg} | -200 to +200 | °C | |

NOTES

- The above specified current will generate a temperature rise of approximately 50°C above ambient temperature in a vacuum environment. Precautions shall be taken to prevent the total temperature of the wire (ambient plus rise) exceeding the continuous operating temperature of the wire.

FIGURE 1 - PARAMETER DERATING INFORMATION

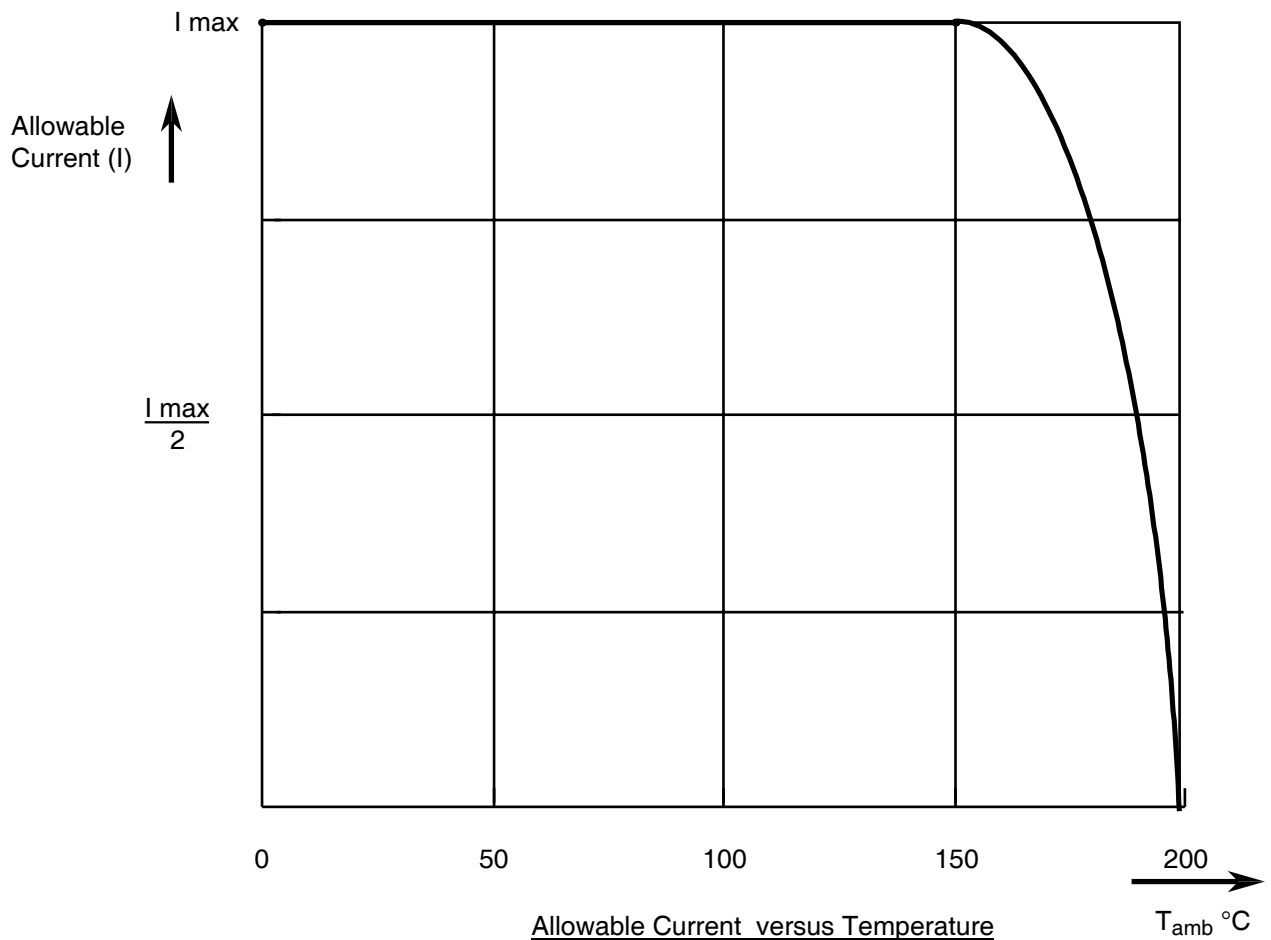

Allowable Current versus Temperature

FIGURE 2 - PHYSICAL CHARACTERISTICS

Dimensions are given in Table 1(a)

FIGURE 2(a) - FINISHED WIRES


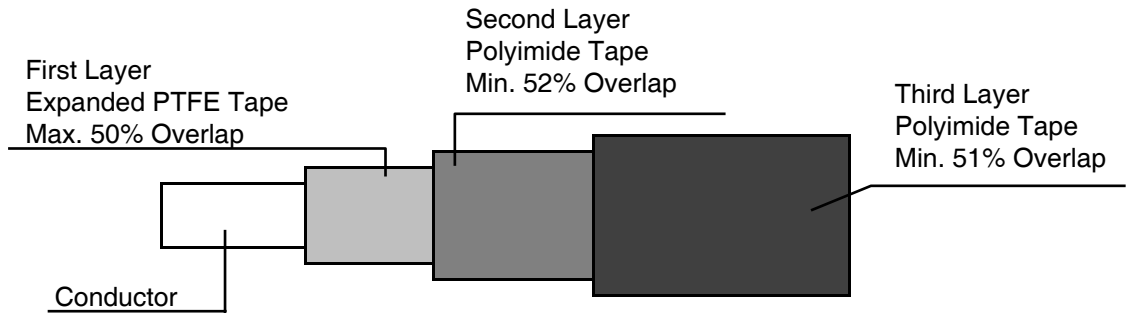



FIGURE 2(b) - MULTICORE CABLE

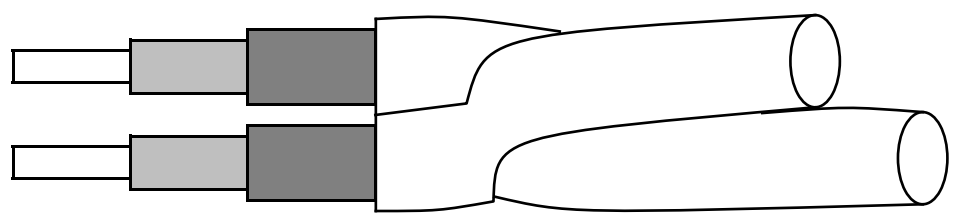

NOTES

1. Finished wire according to Figure 2(a).

FIGURE 2(c) - SHIELDED AND JACKETED CABLES

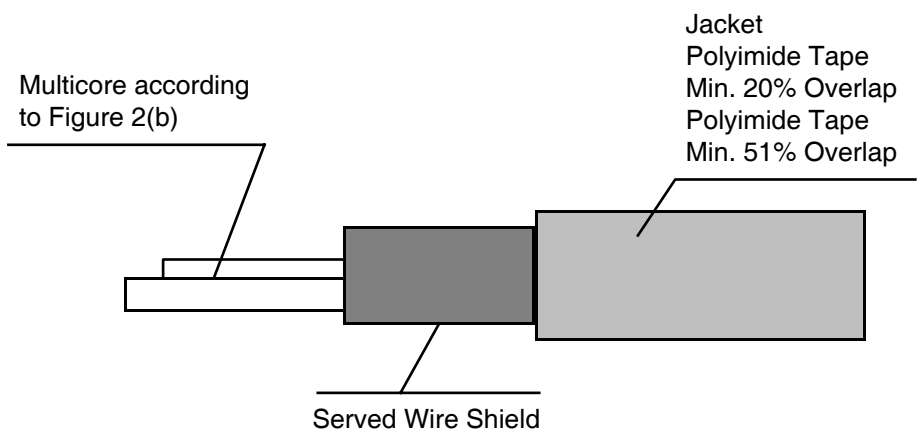

| | | |
|---|---|---|
|  | <p style="text-align: center;">ESCC Detail Specification No. 3901/019</p> | <p style="text-align: right;">PAGE 12 ISSUE 2</p> |
|---|---|---|

2. **APPLICABLE DOCUMENTS**

The following documents form part of this specification and shall be read in conjunction with it:

- ESCC Generic Specification No. 3901, Wires and Cables, Electrical, 600V, Low Frequency.
- MIL-STD-104, Limits for Electrical Insulation Colours.
- ISO 2635, Aircraft - Conductors for General Purpose Aircraft.

3. **TERMS, DEFINITIONS, ABBREVIATIONS, SYMBOLS AND UNITS**

For the purpose of this specification, the terms, definitions, abbreviations, symbols and units specified in ESCC Basic Specification No. 21300 and ESCC Generic Specification No. 3901 shall apply.

4. **REQUIREMENTS**

4.1 **GENERAL**

The complete requirements for procurement of the finished wires and cables specified herein are stated in this specification and ESCC Generic Specification No. 3901. Deviations from the Generic Specification, applicable to this specification only, are listed in Para 4.2.

Deviations from the applicable Generic Specification and this Detail Specification, formally agreed with specific Manufacturers on the basis that the alternative requirements are equivalent to the ESCC requirements and do not affect the components` reliability, are listed in the Appendices attached to this specification.

4.2 **DEVIATIONS FROM GENERIC SPECIFICATION**

4.2.1 **Deviations from Special In-process Controls**

None.

4.2.2 **Deviations from Final Production Tests (Chart II)**

None.

4.2.3 **Deviations from Burn-in Tests (Chart III)**

Not applicable.

4.2.4 **Deviations from Qualification Tests (Chart IV)**

- (a) Para. 9.21, Resistance to Fluids: To be modified in accordance with Para. 4.8.11 of this specification.

4.2.5 **Deviations from Lot Acceptance Tests (Chart V)**

None.

4.3 **MECHANICAL REQUIREMENTS**

4.3.1 **Dimension Check**

The dimensions of the finished wires and cables specified herein shall be checked; they shall conform to those shown in Table 1(a), Figure 2 and Para 4.4 of this specification (see below for the list of parameters to be checked).

LIST OF PARAMETERS TO BE CHECKED

| PARAMETER | TABLE 1(a) | FIGURE 2 | PARA 4.4 |
|---------------------------|------------|----------|----------|
| <u>COMPOSITION</u> | | | |
| Number of conductors | X | | |
| Gauge | X | | |
| Shielding | X | | |
| Jacket | | X | |
| <u>CONDUCTOR</u> | | | |
| Nature | | | X |
| Outer diameter | X | | |
| Number of strands | X | | |
| Strand diameter | X | | |
| Length of lay | | | X |
| Plating Thickness | | | X |
| <u>INSULATION</u> | | | |
| Composition | | X | X |
| Thickness | | | X |
| Concentricity | | | X |
| Outer diameter | X | | |
| Core identification | | | X |
| <u>SHIELDING</u> | | | |
| Number of strands | X | | |
| Type of shielding | | | X |
| Strand diameter | X | | |
| Nature | | X | |
| Shield strand adhesion | | | X |
| Shielding lay | | | X |
| Shield coverage | | | X |
| <u>JACKET</u> | | | |
| Composition | | X | X |
| Protective tape wraps | | X | X |
| Thickness | | | X |
| Overlapping | | | X |
| Outer diameter | X | | |

4.3.2 **Weight**

The maximum weight of the finished wires and cables specified herein shall be as specified in Table 1(a).



4.4 MATERIALS AND FINISHES

The materials and finishes shall be as specified herein. Where a definite material is not specified, a material which will enable the wires and cables specified herein to meet the performance requirements of this specification shall be used. Acceptance or approval of any constituent material does not guarantee acceptance of the finished product.

4.4.1 Conductor

4.4.1.1 Material Characteristics

All strands used in the manufacture of the conductors shall be silver-coated, soft or annealed, oxygen-free high conductivity copper for ISO 004, 006, 012 and 030, and silver-coated high strength copper alloy for ISO 001 and 002 and AWG 28 inclusive.

On silver-coated strands, the thickness of silver shall be 2 microns minimum.

On all copper conductors, any strand shall show a 10% minimum elongation.

For high-strength copper alloy conductors, the tensile characteristics shall be not less than 6% in elongation and 35kg per square mm in tensile strength.

For determination of the conductor resistance at +20°C, as mentioned in Para 9.5 of ESCC Generic Specification No. 3901, the α coefficient for copper alloy is 0.0035.

4.4.1.2 Stranding

The conductors shall be constructed of concentrically laid strands to produce a smooth and uniform conductor of circular cross-section and free from any high strands or other surface irregularities.

The length of lay of the external layer shall not be less than 8, nor more than 16, times the maximum conductor diameter specified in Table 1(a).

4.4.2 Insulation

4.4.2.1 Material

Any insulating material shall be virgin polyimide with only those additives that are necessary for processing and pigmentation.

4.4.2.2 Construction

The insulation shall have a uniform cross-section throughout the length of the cable and the conductor shall be evenly centred in the insulation.

The insulation shall consist of 2 wrapped layers of polyimide tapes as specified in Figure 2(a).

4.4.3 Shield

4.4.3.1 Material

Shield strands shall be silver-coated, annealed copper as specified in Para. 4.4.1.1 of this specification, but the thickness of silver shall be 2.5 microns minimum.

4.4.3.2 Construction

Shields shall be closely and helically wound around the single insulated wire or twisted bundle of insulated wires (core) and provide not less than 92% coverage as calculated by the following formula:



$$K = \frac{n \times d_w \sqrt{(\pi D)^2 + P^2}}{P \pi D} \times 100(\%)$$

- K = coverage (%)
n = number of serving wires
d_w = shield strand diameter (mm)
D = diameter of core (mm)
P = serving pitch (mm)

4.4.4 Jacket

All shielded cables shall be provided with jackets of wrapped polyimide tapes as specified in Figure 2(c). The wrapped tapes shall be heat-sealed. The side of the tape of the first layer above the shield, which is not coated with FEP resin, shall be facing the shield.

4.4.5 Construction of Multicore Cables

Multicore cables shall be constructed by twisting the required number and size of finished wires to form a uniform cable without high strands, bends or other irregularities. Finished wires of only one size shall be used for one cable. The cabling shall be with a left-hand lay and the lay length shall not be less than 12 times and not be more than 16 times the outside diameter of the unshielded unjacketed cable. The construction of shielded and jacketed cables is shown in Figure 2(c). Fillers shall not be used in the construction of multicore cables except for the 5- and 6-core cable, where the 5/6 wires shall be twisted around a round, uncoloured filler made of polytetrafluoroethylene. The diameter of the filler shall be 0.7 times the diameter of the wires used in the cable for the 5-core cable and the same diameter of the finished wire for the 6-core cable.

4.4.6 Colour Coding

4.4.6.1 Finished Wire Colour Coding

The colour of the finished wires shall be the natural colour of the top wrap on the insulation except when colouring is specifically required in the contract.

Colours:

- Black (not to be preferred)
- Brown
- Red
- Orange (not to be preferred)
- Yellow
- Green
- Natural

The colour of top wraps shall conform to the colour limits specified in MIL-STD-104, Class 1.

4.4.6.2 Multicore Cable Colour Coding

If the contract does not define any specific colour coding, all individual cores in multicore cables shall have the natural colour. If colour coding is desired, it is proposed that the individual cores in such cables shall be coloured according to the following scheme:

| No. OF CORES IN CABLE | COLOUR OF RESPECTIVE CORES | | | | | | |
|-----------------------|----------------------------|---------|--------|-------|-------|-------|--------|
| 2 | red | natural | | | | | |
| 3 | red | natural | yellow | | | | |
| 4 | red | natural | yellow | green | | | |
| 5 | red | natural | yellow | green | brown | | |
| 6 | red | natural | yellow | green | brown | black | |
| 7 | red | natural | yellow | green | brown | black | orange |

4.4.6.3 Jacket colour

The colour of jackets shall normally be the natural colour of the polyimide tapes.

4.5 MARKING


4.5.1 General

The marking of all spools of finished wires or cables delivered to this specification shall be in accordance with the requirements of ESCC Basic Specification No. 21700. Each spool shall be marked in respect of:-

- (a) The ESCC Component Number.
- (b) Characteristics.
- (c) Traceability Information.
- (d) Additional Marking.


4.5.2 The ESCC Component Number

Each spool shall bear the ESCC Component Number which shall be constituted and marked as follows:-

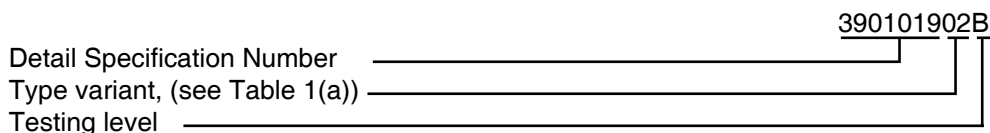

4.5.3 Characteristics

The characteristics shall show the length(s) of the finished wire or cable wound on each spool and shall



NOTES

1. Whenever the length is less than 100 metres, insert a zero in the first block (example: 075 m). If more than one length of finished wire or cable is wound on a spool, the characteristics of each length shall be marked as above.

4.5.4 Traceability Information

Each spool shall be marked in respect of traceability information in accordance with the requirements of ESCC Basic Specification No. 21700.

4.5.5 Additional Marking

Each spool shall bear the Manufacturer`s Quality Control Inspector`s stamp.

4.6 ELECTRICAL MEASUREMENTS

4.6.1 Electrical Measurements at Room Temperature

The parameters to be measured at room temperature are scheduled in Table 2. The measurements shall be performed at $T_{amb} = +22 \pm 3 \text{ }^\circ\text{C}$.

4.6.2 Electrical Measurements at High and Low Temperatures

Not applicable.

4.6.3 Circuits for Electrical Measurements

Not applicable.

4.7 BURN-IN TESTS

Not applicable.

4.8 ENVIRONMENTAL AND ENDURANCE TESTS

4.8.1 Mechanical Properties of Conductor

As detailed in Para. 4.4.1.1 of this specification.

4.8.2 Accelerated Ageing

Ageing Temperature $+230 \pm 5 \text{ }^\circ\text{C}$.

4.8.3 Wrap Test at Ambient Temperature

The mandrel diameters and applied loads for wrap testing of finished wires are given in Table A. The mandrel diameters and applied loads for shielded and jacketed cables are given in Table B.

TABLE A - MANDREL DIAMETERS AND LOADS FOR FINISHED WIRES

| Wire Size ISO / (AWG) | Mandrel Diameter (mm) | Applied Weight (kg) |
|--------------------------|-----------------------|---------------------|
| - / (30) | 5.0 | 0.15 |
| - / (28) | 6.0 | 0.25 |
| 001 / (26) | 6.0 | 0.25 |
| 002 / (24) | 6.0 | 0.25 |
| 004 / (22) | 6.0 | 0.40 |
| 006 / (20) | 6.0 | 0.40 |
| 012 / (16) | 10 | 0.50 |
| 030 / (12) | 20 | 1.00 |



TABLE B - MANDREL DIAMETERS AND LOADS FOR SHIELDED AND JACKETED CABLES

| CABLE SIZE ISO /(AWG) | NUMBER OF CORES | MANDREL DIAMETER (mm) | APPLIED WEIGHT (kg) |
|--------------------------|--------------------|-----------------------------|---------------------------|
| - / (30) | 1 | 8.0 | 0.15 |
| - / (28) | 1 | 8.0 | 0.25 |
| 001 / (26) | 1 | 10 | 0.25 |
| 002 / (24) | 1 | 12 | 0.25 |
| 004 / (22) | 1 | 15 | 0.50 |
| 006 / (20) | 1 | 15 | 0.50 |
| 012 / (16) | 1 | 20 | 1.00 |
| 030 / (12) | 1 | 20 | 1.00 |
| - / (30) | 2 | 10 | 0.25 |
| - / (28) | 2 | 10 | 0.50 |
| 001 / (26) | 2 | 15 | 0.50 |
| 002 / (24) | 2 | 15 | 0.50 |
| 004 / (22) | 2 | 20 | 0.80 |
| 006 / (20) | 2 | 20 | 0.80 |
| 012 / (16) | 2 | 25 | 1.00 |
| 030 / (12) | 2 | 30 | 1.00 |
| - / (30) | 3 | 12 | 0.25 |
| - / (28) | 3 | 12 | 0.50 |
| 001 / (26) | 3 | 15 | 0.75 |
| 002 / (24) | 3 | 15 | 0.75 |
| 004 / (22) | 3 | 20 | 1.20 |
| 006 / (20) | 3 | 20 | 1.20 |
| 012 / (16) | 3 | 30 | 1.50 |
| 030 / (12) | 3 | 40 | 1.50 |
| - / (30) | 4 | 15 | 0.50 |
| - / (28) | 4 | 15 | 0.80 |
| 001 / (26) | 4 | 15 | 1.00 |
| 002 / (24) | 4 | 20 | 1.00 |
| 004 / (22) | 4 | 20 | 1.50 |
| 006 / (20) | 4 | 25 | 1.50 |
| 012 / (16) | 4 | 30 | 1.50 |
| 030 / (12) | 4 | 40 | 1.50 |
| - / (28) | 5 | 15 | 1.00 |
| 001 / (26) | 5 | 20 | 1.50 |
| 002 / (24) | 5 | 20 | 1.50 |
| 004 / (22) | 5 | 25 | 2.00 |
| 006 / (20) | 5 | 30 | 2.00 |
| - / (28) | 6/7 | 20 | 1.00 |
| 001 / (26) | 6/7 | 20 | 1.50 |
| 002 / (24) | 6/7 | 20 | 1.50 |
| 004 / (22) | 6/7 | 25 | 2.00 |
| 006 / (20) | 6/7 | 30 | 2.00 |

4.8.4 Voltage Test

No particular conditions are applicable.

4.8.5 Shrinkage

The shrinkage temperature shall be $+200 \pm 5$ °C

4.8.6 Blocking

The blocking temperature shall be $+230 \pm 5$ °C.

4.8.7 Cold Bend Test

The mandrel diameters and loads shall be as specified in Table C.

TABLE C - MANDREL DIAMETERS AND LOADS FOR FINISHED WIRES OR CORES

| Wire Size ISO / (AWG) | Mandrel Diameter (mm) | Applied Weight (kg) |
|--------------------------|-----------------------|---------------------|
| - / (30) | 5.0 | 0.15 |
| - / (28) | 6.0 | 0.25 |
| 001 / (26) | 6.0 | 0.25 |
| 002 / (24) | 6.0 | 0.25 |
| 004 / (22) | 6.0 | 0.40 |
| 006 / (20) | 6.0 | 0.40 |
| 012 / (16) | 10 | 0.50 |
| 030 / (12) | 20 | 1.00 |

4.8.8 Cut-through Resistance

The mean load measured during 9 tests shall not be less than the relevant value specified below:-

| Wire Size ISO Requirements | - | - | 001 | 002 | 004 | 006 | 012 | 030 |
|-------------------------------|------|------|------|------|------|------|------|------|
| (AWG) | (30) | (28) | (26) | (24) | (22) | (20) | (16) | (12) |
| Cut-through Load (kg) | 9.0 | 11 | 11 | 11 | 25 | 32 | 35 | 50 |

4.8.9 Notch Resistance

The depth of notch shall be 0.04mm.

4.8.10 Flammability Resistance

No particular conditions are applicable.

4.8.11 Resistance to Fluids

Tests (h), (i) and (j) shall not be performed.

4.8.12 Surface Resistance

No particular conditions are applicable.

4.8.13 Abrasion Resistance

The weight to be applied to the needle is specified below:-

| | | | | | | | | |
|-----------------------------------|------|------|------|------|------|------|------|------|
| Wire Size ISO Requirements | - | - | 001 | 002 | 004 | 006 | 012 | 030 |
| (AWG) | (30) | (28) | (26) | (24) | (22) | (20) | (16) | (12) |
| Scrape Abrasion (Load in grammes) | 350 | 500 | 650 | 750 | 800 | 900 | 1050 | 1200 |

4.8.14 Soldering

No particular conditions are applicable.

4.8.15 Solderability

No particular conditions are applicable.

4.8.16 Radiation Resistance

No particular conditions are applicable.

4.8.17 Overload Resistance

No particular conditions are applicable.

4.8.18 Outgassing in Vacuum

No particular conditions are applicable.

4.8.19 Long-term Ageing Test

The long-term ageing temperature shall be +200°C.

TABLE 2 - ELECTRICAL MEASUREMENTS AT ROOM TEMPERATURE

| NO | CHARACTERISTICS | SPECIFICATION AND TEST METHOD | TEST CONDITION | LIMITS | UNIT |
|----|-----------------------|-------------------------------|----------------|-------------------------------|-------|
| 1 | Conductor Resistance | ESCC No. 3901, Section 9 | Para 9.5 | Table 1(a) | Ω/km |
| 2 | Spark Test | ESCC No. 3901, Section 9 | Para 9.6 | Insulation: 3 Jacket: 1.5 | kV |
| 3 | Voltage Test | ESCC No. 3901, Section 9 | Para 9.7 | Para 9.7 | kV |
| 4 | Insulation Resistance | ESCC No. 3901, Section 9 | Para 9.8 | Insulation: 750 Jacket: 30 | MΩ.km |
| 5 | Surface Resistance | ESCC No. 3901, Section 9 | Para 9.22 | 125 | MΩ.mm |